arXiv:0806.1663v1 [cond-mat.supr-con] 10 Jun 2008

Discovery of a predominant paramagnetic Meissner effect in superconducting dichalcogenides

R. Miller,[1] S. Altmannshofer,[1] E.–W. Scheidt,[1] M. Herzinger,[1] C. Gold,[1] F. Mayr,[2] D. Einzel,[3] and W. Scherer[1, *]

[1]*CPM, Institut für Physik, Universität Augsburg, 86135 Augsburg, Germany*
[2]*EP V – EKM, Institut für Physik, Universität Augsburg, 86135 Augsburg, Germany*
[3]*Walther-Meissner-Institut für Tieftemperaturforschung, 85748 Garching, Germany*

(Dated: June 10, 2008)

We report on the electronic and thermodynamic properties of the new superconducting hybrid 18R-$SnSe_2\{CoCp_2\}_{0.1}$ ($T_c = 6$ K). Field-cooled (FC) ac- and dc-susceptibility measurements in low magnetic fields up to 1 mT reveal a predominant paramagnetic Meissner effect ($>27\%$ of the amount of the full diamagnetic signal). This anomalous paramagnetic response occurs unexpectedly even in zero-field-cooled (ZFC) sequences. Furthermore, our experimental findings favor an intrinsic and reversible occurrence of spontaneous magnetization at $T < T_c$. These observations disfavor the alternative scenario of extrinsic trapping of magnetic flux.

The highly anisotropic electronic properties of quasi-two-dimensional (2D) intercalation complexes of transition metal dichalcogenides have been extensively studied since their discovery [1]. Already, the non-intercalated parent systems, e. g., 2H-$TMSe_2$, 2H-TMS_2 (TM = Nb, Ta) stimulated intensive research activity since they are characterized by phase diagrams where inherent superconductivity and charge density-wave (CDW) order coexist at low temperatures [2, 3]. Hence, layered dichalcogenides might serve as model systems for the understanding of other highly correlated electronic systems, such as the high-T_c cuprate superconductors (HTSC) [4]. An important milestone in this respect was reached by Gamble *et al.* [5] who reported a dramatic increase in T_c of TaS_2 when the host lattice was intercalated with the organic donor pyridine, while Schaak *et al.* showed that T_c of the recently discovered superconducting layered sodium cobalt oxyhydrate, $Na_xCoO_2{\cdot}1.3H_2O$ [6] displays the same kind of behavior on chemical doping that is observed in HTSCs. Furthermore, O'Hare and coworkers found that semiconducting 2H-$SnSe_2$ renders in a superconducting hybrid upon intercalation of the organometallic donor molecule cobaltocene, $CoCp_2$ ($Cp = C_5H_5$), to produce 2H-$SnSe_2(CoCp_2)_{0.33}$ [7]. Hence, intercalation of dichalcogenides with electron-rich metallocenes [8] provides a powerful way to finely tune the electronic properties of these highly anisotropic solids via *charge transfer* and *increased interlayer separation*.

In this report, we show that nano structuring via *staging-controlled intercalation* of cobaltocene – as exemplified by the new layered superconductor 18R-$SnSe_2\{CoCp_2\}_{0.1}$ ($T_c = 6$ K) – might provoke anisotropic properties such as the paramagnetic Meissner effect (PME). This effect, also referred to as Wohlleben effect, has hitherto not been reported for dichalcogenides, but for some layered cuprates [9] and conventional superconductors [10]. Hence, the related highly anisotropic superconducting properties of 18R-$SnSe_2\{CoCp_2\}_{0.1}$ and the layered cuprates might allow us to investigate the microscopic origin and nature of the Wohlleben effect in these 2D systems.

A single crystalline 18R-$SnSe_2$ sample ($\approx$ 2 cm $\times$ 1 cm $\times$ 0.1 mm) was synthesized by chemical vapor transport and intercalated with cobaltocene in acetonitrile at 65 °C (21 days). The composition with respect to the Sn, Se, and Co content was analyzed by ICP-OES yielding $SnSe_{1.99}\{CoCp_2\}_{0.1}$. A single-crystal X-ray study at 6 K clearly demonstrates that intercalation of the 18R-$SnSe_2$ host-lattice with cobaltocene results in a 3rd stage hybrid material ($\varrho = 4.9$ g/cm^3), which is in agreement with an elongation of the c-axis from 55.26 Å to 71.6 Å (Fig. 1). For more details see the Supplement [11].

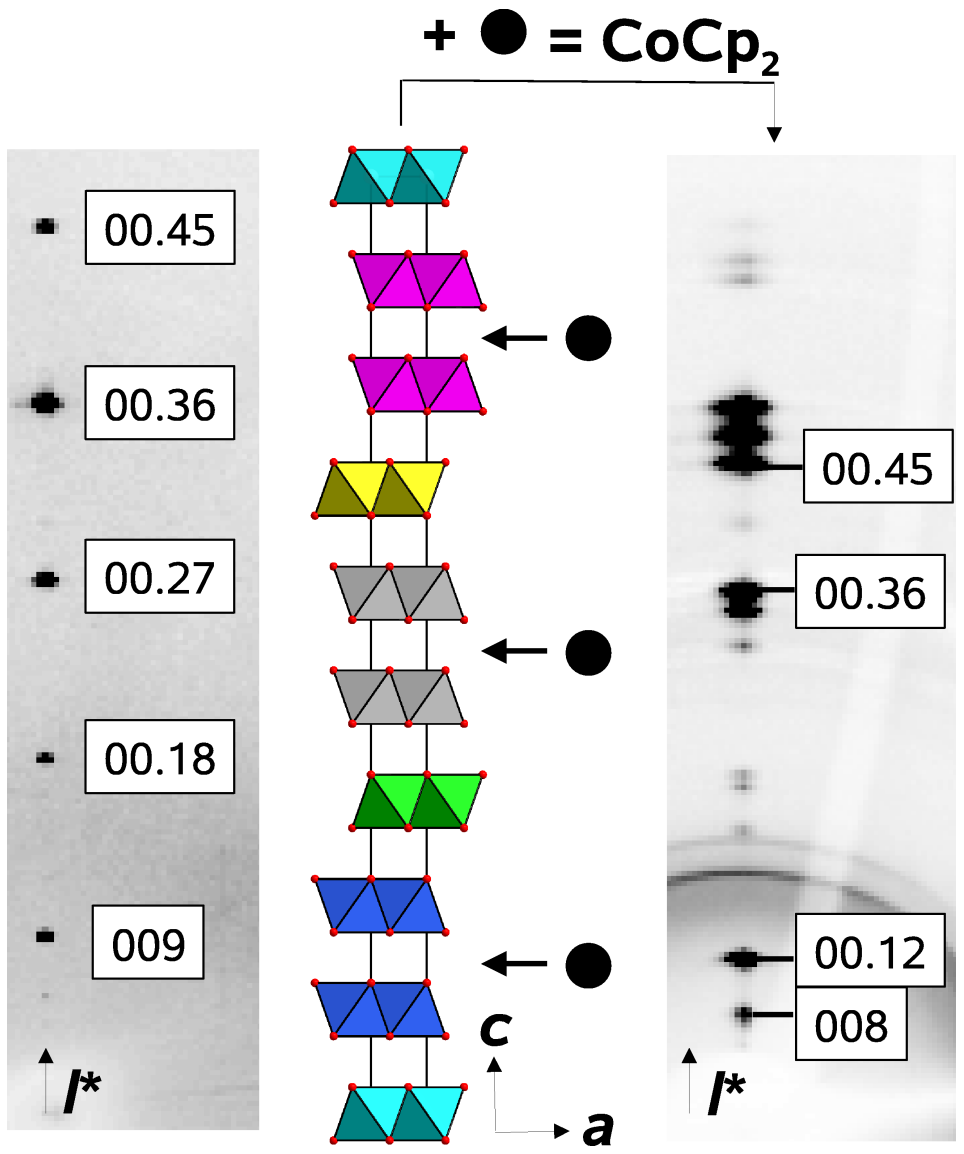

FIG. 1: (Color online) Reciprocal space reconstruction based on single crystal X-ray data of 18R-$SnSe_2$ (RT; left) and of the intercalated species ($T = 6$ K; right) along the 00l* axis. Intercalation of 18R-$SnSe_2$ with cobaltocene, $CoCp_2$, causes a lattice expansion along the c-axis from 55.26 Å to 71.6 Å in agreement with the formation of a 3rd stage hybrid material where each third interlayer is totally occupied by $CoCp_2$ molecules (idealized model).

In the following we present a short introduction of the PME, which was observed for the first time in polycrystalline samples of the HTSC $Bi_2Sr_2CaCu_2O_{8-\delta}$ [9]. The best way to identify the PME is to perform magnetic field studies employing zero-field-cooled (ZFC) and field-cooled (FC) measurements. The sequences of the ZFC and FC procedures are illustrated in a schematic B-T phase diagram (Fig. 2(a)). ZFC

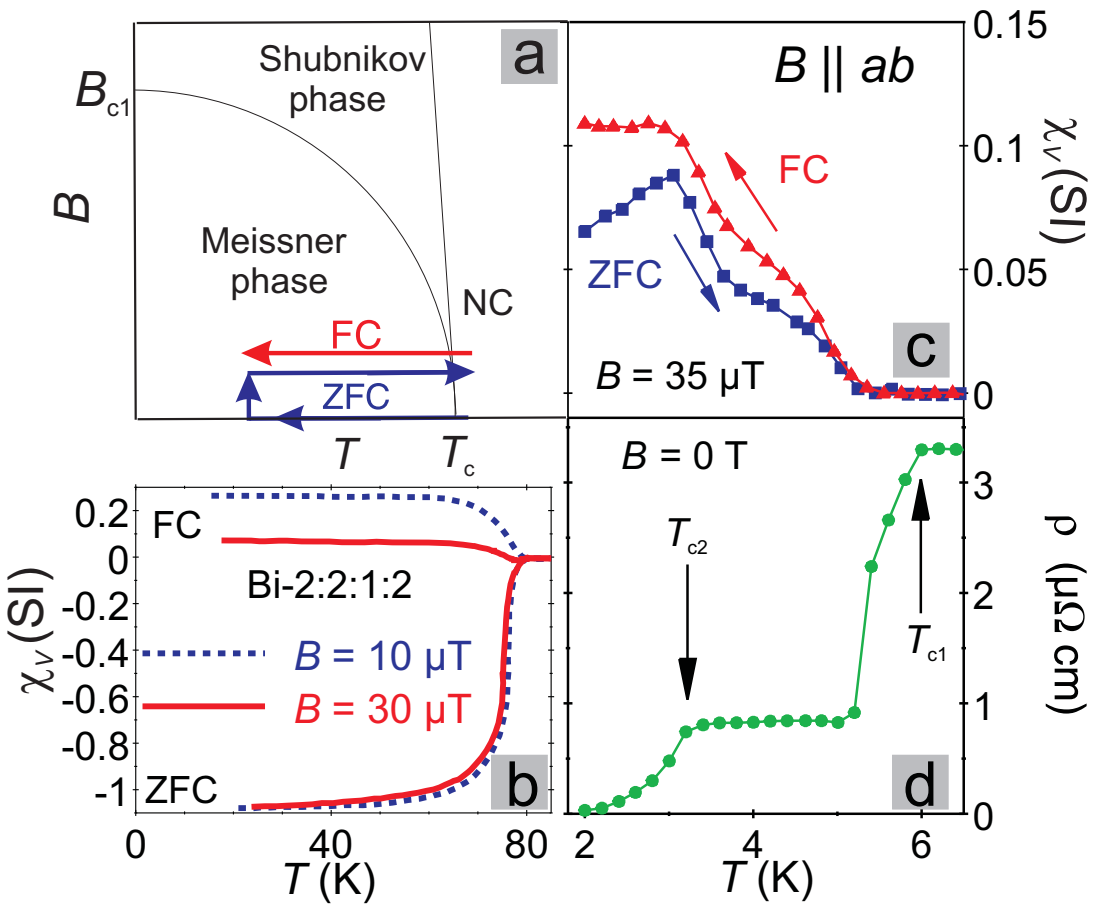

FIG. 2: (Color online) (a) Schematic sketch of the ZFC and FC sequences in a B-T phase diagram; (b) ZFC and FC susceptibility of Bi-2:2:1:2 (from Ref. 12); (c) Extraordinary Wohlleben effect in $\chi(T)$ ZFC and FC sequences with B parallel to the ab-planes of 18R-SnSe$_2$$\{$CoCp$_2\}_{0.1}$; (d) $\rho(T)$ parallel to the ab-planes in zero magnetic field.

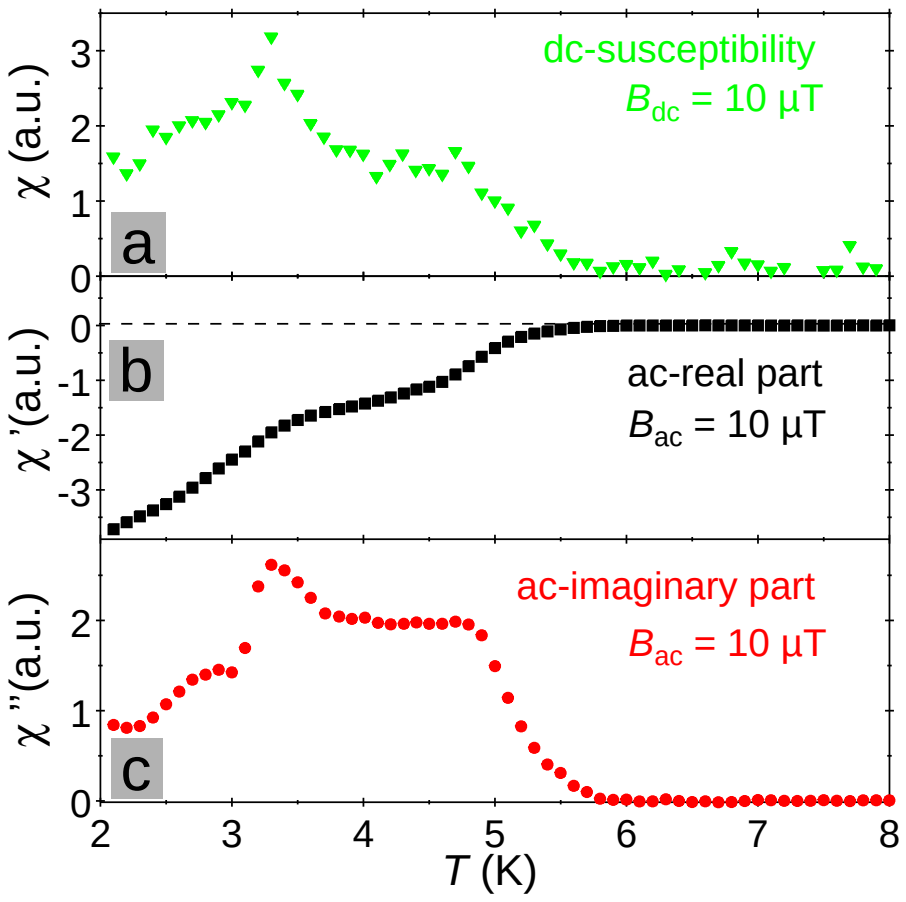

FIG. 3: (Color online) Comparison between (a) dc- and (b,c) ac-susceptibility measurements; the sample has been cooled in an external magnetic field of 10 μT.

sequences in low magnetic fields usually result in a complete shielding effect at low temperatures ($\chi_V \cong -1$), whereas the FC curves exhibit paramagnetic behavior, which decreases with increasing field due to an enhancement of the diamagnetic contribution. Such shielding behavior is seen in Fig. 2(b) in the case of Bi-2:2:1:2-samples by Wohlleben and coworkers [12]. The PME was first attributed to spontaneous formation of current loops caused by π-junctions in weak links between domain boundaries, which are aligned in small external magnetic fields. Later, the PME was also found in single-crystalline YBa$_2$Cu$_3$O$_{7-\delta}$ [13]. Several controversial concepts are proposed to elucidate the nature and origin of the PME (for an overview, see Ref. 14). Here we will discuss the first example of an anisotropic Wohlleben effect, where even the ZFC sequences in 18R-SnSe$_2$$\{$CoCp$_2\}_{0.1}$ curves exhibit a paramagnetic response.

In Fig. 2(c) ZFC and FC dc-susceptibility curves of SnSe$_{1.99}$$\{$CoCp$_2\}_{0.1}$ in a small external magnetic field [15] of $B = 35\,\mu$T are displayed. Below a first superconducting transition ($T_{c1} = 6$ K) paramagnetic behavior is observed for both pathways, ZFC and FC. The latter directly signals the presence of a PME. However, the paramagnetic response when applying a small magnetic field after ZFC is unexpected and is therefore denoted in the following as an unprecedented Wohlleben effect. Around 3.7 K an additional contribution to the paramagnetic behavior is observed, which might arise from an anisotropic bulk Wohlleben effect characterized by a different extent parallel and perpendicular to the ab-planes. We further note that also the resistivity data corroborate the presence of an anisotropic superconducting state. In Fig. 2(d) the resistivity parallel to the ab-planes clearly exhibits that the sample undergoes two superconducting transitions, at $T_{c1} = 6$ K and $T_{c2} = 3.3$ K associated with in-plane and out-of-plane superconductivity, respectively. We suggest that dislocations between intercalated and native SnSe$_2$ double layers (see Fig. 1 and [11]) are responsible for the presence of two superconducting transitions. At $T_{c1} = 6$ K no continuous in-plane superconducting path in the resistivity is available. It is therefore conceivable that the steps have their physical origin in a percolation process occurring in the intercalated SnSe$_2$ *ab*-sheets and bridging selenium atoms of neighboring layers staged along the out-of-plane *c*-direction.

Since the Wohlleben effect itself describes a rather unusual paramagnetic behavior, we have to rule out the presence of other paramagnetic contributions carefully. In the following, we discuss possible origins of the paramagnetic response which may coexist with a superconducting phase. First, we analyzed whether the paramagnetic increase at low temperatures could be due to a Curie contribution. If we consider the fact that CoCp$_2$ donor-molecules have only partially transferred their unpaired *d*-electron to the conduction band the only origin of a Curie term could be attributed to the ^{2}E$_{1g}$ state of neutral CoCp$_2$. However, even the volume susceptibility of pure CoCp$_2$ (χ(SI) = 9.2 × 10^{-3} at $T = 2$ K) in comparison with the FC susceptibility of SnSe$_{1.99}$$\{$CoCp$_2\}_{0.1}$ (see Supplement [11]) is by a factor of 17 smaller, which rules out such possibility. Second, from susceptibility measurements in a magnetic field of 1 T we can also exclude any other spin-paramagnetic impurities [11]. On the contrary, from these measurements one receives an effective magnetic moment of $\mu_{\rm eff} = 0.03\,\mu_{\rm B}$, which indicates that more than 98 % of all CoCp$_2$ molecules transfer their unpaired electron to the conduction band of the SnSe$_2$-layers (for a detailed calculation, see Ref. 16). This result is different from the conclusion drawn by O'Hare for 2H-SnSe$_2$$\{$CoCp$_2\}_{0.31}$ where a charge transfer of only 78 % was assumed [17]. Third, we can rule out the presence of spin-paramagnetic fluctuations. Even during long measuring intervals (three days) we cannot identify within the

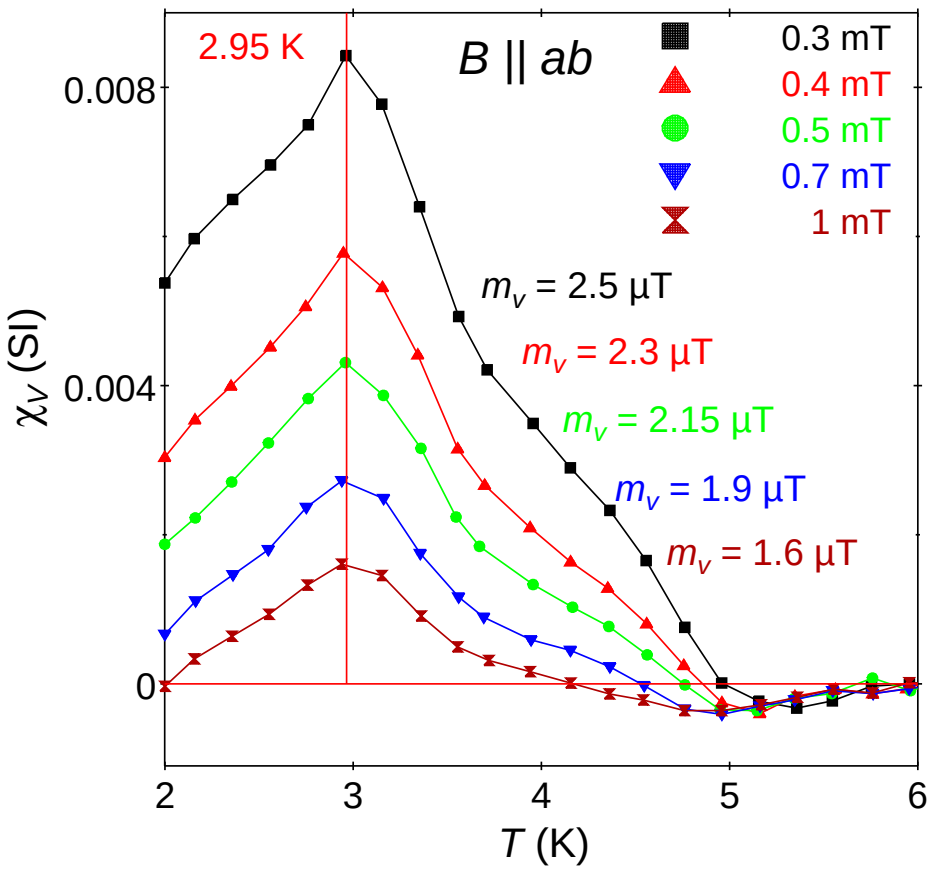

FIG. 4: (Color online) FC susceptibility measurements in various magnetic fields; the maximal volume magnetizations m_V are obtained at 2.95 K and displayed in ascending order of the magnitude of the applied magnetic fields; with increasing magnetic field m_V decreases, whereas the maximum shifts slightly to lower temperature. This is in line with the Wohlleben effect.

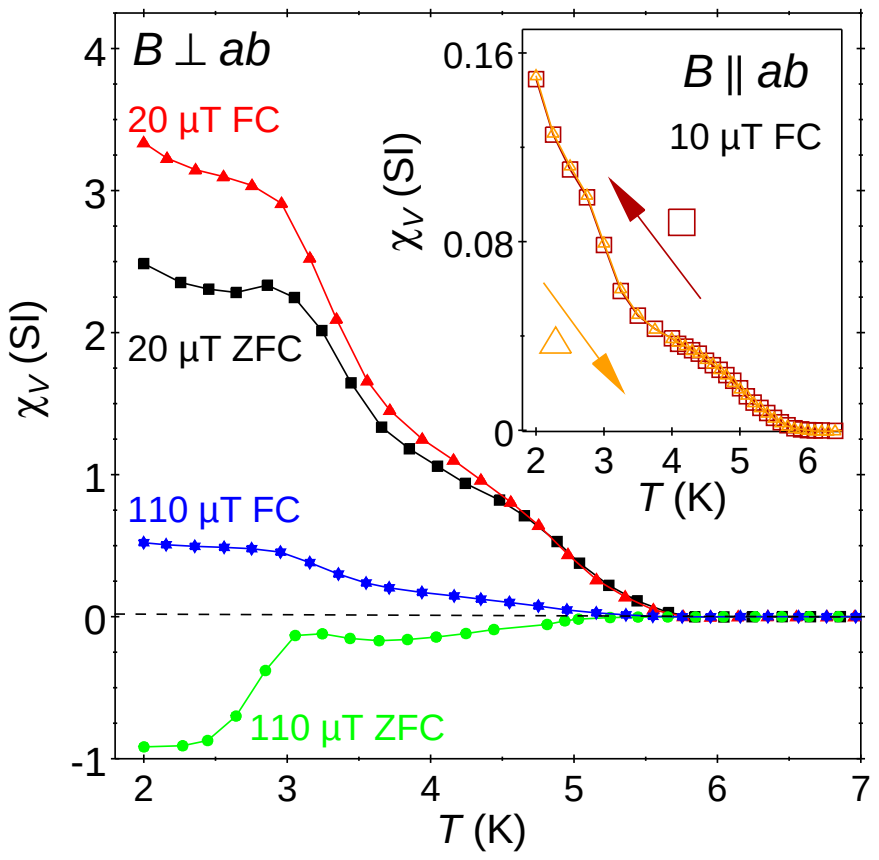

FIG. 5: (Color online) ZFC and FC volume susceptibility curves with B perpendicular to the ab-planes. The data are corrected with a demagnetization factor of $N = 0.78$ (see [11]). The insert exhibits reversal FC cooling and FC warming sequences with B parallel to the ab-planes (for details see [11]).

error bar of 0.5 % any relaxation of the paramagnetic moment at $T = 3$ K [11].

To verify that the paramagnetic ZFC and FC susceptibilities are observed within the superconducting state and to clarify whether the double structure observed in the dc-susceptibility (Fig. 2(c)) can be attributed to an anisotropic PME we performed simultaneously dc- and ac-susceptibility measurements, which have been recorded after FC ($B = 10\mu$T). In Fig. 3(a) the dc-susceptibility $\chi(T)$ again shows a clear paramagnetic double feature in the superconducting regime, whereas in the same temperature region the ac-susceptibility exhibits two superconducting transitions (Figs. 3(b),(c)) which are clearly correlated with the two individual paramagnetic signals in Fig. 3(a). Thus, the two superconducting transitions provide strong evidence for the presence of an anisotropic Wohlleben effect. The plateau in χ''_{ac} between the two superconducting transitions may be due to strong superconducting fluctuations. In detail, at the first transition superconductivity within the layers is paralleled by an in-plane PME, whereas at the second transition superconductivity perpendicular is accompanied by an out-of-plane PME.

For a thorough investigation in the framework of the Wohlleben effect we performed detailed FC-susceptibility studies in several external magnetic fields (Fig. 4). The paramagnetic contribution is decreasing with increasing field. These findings are in accord with the Wohlleben effect as interpreted by Sigrist and Rice [18]. They predict a constant paramagnetic fraction, whereas the diamagnetic shielding increases with increasing magnetic field. For the temperature-dependent susceptibility an increasing diamagnetic contribution with increasing magnetic field is seen between 4.5 K and 5.5 K. When the temperature is lowered spontaneous eddy-currents emerge associated with a positive magnetization. Therefore, the paramagnetic signal sets in a few tenths of a degree below the onset of the normal Meissner effect [18]. The point of inflection around 3.5 K displays the onset of the second superconducting transition, which again reveals the second PME transition. Furthermore, the decrease of the susceptibility below 2.95 K may be associated with an underlying broad superconducting transition, which is due to an extremely large out-of-plane penetration depth ($\lambda_{\rm L} \approx 1\mu$m) in comparison to the sample thickness. It is important to note that the initial occurrence of the Meissner effect can only be observed for high quality single-crystalline samples because in inhomogeneous samples the interplay between the normal and the paramagnetic Meissner effect is obscured.

Naturally, the question arises whether the observed superconductivity accompanied by a Wohlleben effect is a surface or a bulk effect. Therefore, we determined also the volume susceptibility for the ZFC and FC curves in various magnetic fields for $B \perp ab$ (Fig. 5). As already discussed for $B \parallel ab$ an unprecedented and even larger Wohlleben effect is also observed for $B \perp ab$ ($B = 20\,\mu$T). We note that this Wohlleben effect ($\chi_V \approx 3.5$) is by one order of magnitude larger than in other reported compounds. For $B \geq 110\,\mu$T the ZFC curve shows nearly complete shielding ($\chi_V \approx -0.9$) already at 2 K indicating bulk-superconductivity, which is a clear evidence that the Wohlleben effect in 18R-SnSe$_2\{$CoCp$_2\}_{0.1}$ is a bulk effect. In addition, bulk-superconductivity is also verified by a BCS-like hump seen in our specific heat studies (see Supplement [11]).

Our experimental results of the susceptibility, resistivity and specific heat measurements [11] at very low magnetic fields confirm the presence of the Wohlleben effect in 18R-SnSe$_{1.99}\{$CoCp$_2\}_{0.1}$. From a theoretical point of view there exist two main mechanisms in literature for this enigmatic phenomenon which contradict each other: flux trapping [19] and the appearance of spontaneous magnetic moments [18]. In the following these two models are discussed with special respect to our system:

i) In conventional superconductors the PME was found in some Nb-discs [10, 20], where the Wohlleben effect was attributed to the flux trapping mechanism [19]. This model, which was later also applied to high T_c superconductors, is due to either an inhomogeneous superconducting transition or flux trapping inside the giant vortex state [21]. It connects the PME directly to the nature of the surface texture. When the surface-layers are removed, the samples do no longer display a PME [10, 22]. In addition, the PME was attributed to the surface superconductivity, when T_c of the surface is different from the bulk superconducting transition temperature [10]. Theoretical studies for this scenario pointed out that the magnitude of the paramagnetic signal is sensitive to the sample geometry and should be limited to the maximum of 27 % of the absolute amount of the diamagnetic signal (χ_V = -1) but will generally be smaller [19].

ii) Sigrist and Rice [18] proposed an alternative model based on spontaneous appearance of large internal magnetic moments for the occurrence of the PME. This model is in particular applicable to explain the positive magnetization also in ZFC curves which might account for the bulk PME in our samples as well. For HTSC d-wave paring of $d_{x^2-y^2}$-symmetry is assumed. This model was supported experimentally by Magnusson *et al.*, who reported large internal magnetic moments in $\mathrm{Bi_2Sr_2CaCu_2O_8}$ employing FC sequences [23].

Our observations disfavor scenario i). In our system the paramagnetic signal is by more than one order of magnitude higher than that predicted by [19]. Furthermore, the anisotropic character of the Wohlleben effect clearly confirms the bulk character which again contradicts the influence of surface morphology as origin of the PME. Also the unexpected PME in ZFC sequences is not in line with the flux trapping model. Cycling through T_c in FC mode and subsequent warming up in the same mode with different cooling rates occurs fully reversible (see inset of Fig. 5) and displays an increase of the paramagnetic moment with decreasing cooling rate as expected for scenario ii) (for a detailed discussion see the supplementary material [11]). However, it is questionable, if scenario ii) can be used to describe our system, since d-wave pairing symmetry is unlikely to occur in tin diselenide layers.

In summary, a comprehensive PME model which also accounts for our results has to incorporate the spontaneous appearance of large internal magnetic moments in the sample below T_c. We propose that the cobaltocene donor molecules, which are intercalated into the layered structure of 18R-$\mathrm{SnSe_{1.99}\{CoCp_2\}_{0.1}}$ play a key role for the presence of these large internal magnetic moments, a phenomenon only observed in d-wave superconductors so far. Our dc-susceptibility measurements clearly confirm the bulk character of the PME which occurs in our case as an anisotropic effect with a distinct paramagnetic contribution within the superconducting layers and a more pronounced effect perpendicular to them, which can be easily suppressed by a magnetic field. Furthermore, our studies exhibit a PME in ZFC as well as in FC procedures which we have therefore termed an unprecedented paramagnetic Meissner effect. This is very unusual since this effect has only been seen in the FC procedures up to now. So far no theoretical concept exists, which describes the PME in superconductors lacking d-wave symmetry in terms of a bulk effect with predominant internal magnetic moments $>27\%$ of the amount of the full diamagnetic signal. This warrants further exploration by theoretical studies.

We like to thank Prof. M. Sigrist and Prof. T. Kopp for fruitful discussions. This work was supported by NanoCat (R. M.), an International Graduate Program within the Elitenetzwerk Bayern and the DFG (Deutsche Forschungsgemeinschaft) priority programm SPP 1178.

---

[*] Electronic address: Wolfgang.Scherer@Physik.Uni-Augsburg.de

[1] For a review, see R. H. Friend and A. D. Yoffe, Adv. Phys. **36**, 1 (1987).
[2] For a review, see J. A. Wilson and A. D. Yoffe, Adv. Phys. **18**, 193 (1969).
[3] A. H. Castro Neto, Phys. Rev. Lett. **86**, 4382 (2001).
[4] V. Vescoli *et al.*, Phys. Rev. Lett. **81**, 453 (1998).
[5] F. R. Gamble *et al.*, Science **168**, 568 (1970).
[6] R. E. Schaak *et al.*, Nature **424**, 527 (2003).
[7] C. A. Formstone *et al.*, Chem. Commun. **6**, 501 (1990).
[8] M. B. Dines, Science **188**, 1210 (1975).
[9] P. Svedlindh *et al.*, Physica C **162-164**, 1365 (1989).
[10] P. Kostić *et al.*, Phys. Rev. B **53**, 791 (1996).
[11] See EPAPS Document No. for supplementary information, including figures and text regarding synthesis and X-ray data of $\mathrm{SnSe_2}$ and 18R-$\mathrm{SnSe_{1.99}\{CoCp_2\}_{0.1}}$. Furthermore, continuative susceptibility and specific heat studies are shown. A direct link to this document may be found in the online article's HTML reference section.
[12] W. Braunisch *et al.*, Phys. Rev. Lett. **68**, 1908 (1992).
[13] S. Riedling *et al.*, Phys. Rev. B **49**, 13283 (1994).
[14] W. A. Ortiz *et al.*, Physica C **361**, 267 (2001).
[15] For applying the low magnetic fields ($B \leq 100$ μT) we quenched the superconducting magnet before each measurement and checked the resulting magnetic field by an external Gauss-meter, yielding an error of $B \leq 1\mu$T.
[16] R. Miller *et al.*, Phys. Rev. B **73**, 165113 (2006).
[17] D. O'Hare *et al.*, Inorg. Chem. **27**, 1537 (1988).
[18] M. Sigrist and T. M. Rice, *J. Phys. Soc. Jpn.* **61**, 4283 (1992); Rev. Mod. Phys. **67**, 503 (1995).
[19] A. E. Koshelev and A. I. Larkin, Phys. Rev. B **52**, 13559 (1995).
[20] D. J. Thompson *et al.*, Phys. Rev. Lett. **75**, 529 (1995).
[21] M. S. Li, Phys. Rep. **376**, 133 (2003).
[22] R. Lucht *et al.*, Phys. Rev. B **52**, 9724 (1995).
[23] J. Magnusson *et al.*, Physica C **297**, 317 (1998).